

AD-A119 458 AKRON UNIV OH INST OF POLYMER SCIENCE
SLOW DECOMPOSITION OF SILICONE RUBBER. (U)
SEP 82 P VONDRAK, A N SENT
UNCLASSIFIED TR-19

AKRON UNIV OH INST OF POLYMER SCIENCE
SLOW DECOMPOSITION OF SILICONE RUBBER. (U)
SEP 82 P VONDRACEK, A N SENT

F/G 11/10

UNCLASSIFIED

TR-19

N00014-76-C-0408
NL

END
DATE
FORMED
0 82
DUE

AD A119458

12

OFFICE OF NAVAL RESEARCH
Contract N00014-76-C-0408
Project NR 092-555

Technical Report No. 19

SLOW DECOMPOSITION OF SILICONE RUBBER

by

P. Vondracek and A. N. Gent

Institute of Polymer Science
The University of Akron
Akron, Ohio 44325

September, 1982

Reproduction in whole or in part is permitted
for any purpose of the United States Government

Approved for Public Release; Distribution Unrestricted

DTIC
ELECTE
SEP 22 1982
S D H

DTIC FILE COPY

82 09 22 006

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER Technical Report No. 19	2. GOVT ACCESSION NO. AD-A119 458	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Slow Decomposition of Silicone Rubber		5. TYPE OF REPORT & PERIOD COVERED Technical Report
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) P. Vondracek and A. N. Gent		8. CONTRACT OR GRANT NUMBER(s) N00014-76-C-0408
9. PERFORMING ORGANIZATION NAME AND ADDRESS Institute of Polymer Science The University of Akron Akron, Ohio 44325		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 092-555
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Power Program Arlington, VA 22217		12. REPORT DATE September, 1982
		13. NUMBER OF PAGES 27
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report) Unclassified
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) According to attached distribution list. Approved for public release; distribution unrestricted.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES Submitted for publication in: Journal of Applied Polymer Science.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Ageing, Decomposition, Hydrolysis, Rubber, Silicone rubber.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The sol content of previously-extracted samples of lightly-crosslinked silicone rubber has been found to increase during prolonged storage under relatively mild conditions. Simultaneously, the tensile stress slowly decreases in samples held stretched, and one equilibrium degree of swelling increases somewhat. Thus, the polymer network appears to undergo slow decomposition. This process is accelerated by moisture, by ammonia vapor and by raising the temperature of storage. It is slowed down by prior treatment of the polymer with a (continued on reverse side)		

DD FORM 1473
1 JAN 73

EDITION OF 1 NOV 65 IS OBSOLETE
S/N 0102-LF-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

20. ABSTRACT (continued)

silazane reagent which reduces the number of residual OH groups. It is therefore attributed to hydrolytic decomposition of the polydimethylsiloxane molecules, initiated by OH groups.

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist. Special	
A	



1. Introduction

Silicone rubber is generally considered to be stable under mild conditions (1-3). It is regarded as one of the most weather-resistant elastomers, even though some lowering of the mechanical properties has been reported after storage in the open air for several years (1) or after long-term implantation in the human body (4). Recently, however, we have observed the spontaneous adhesion of crosslinked silicone rubber to various substrates (5). This bonding process appeared to be associated with OH groups generated by hydrolytic decomposition of silicone rubber under relatively mild conditions. A detailed study has therefore been carried out of the chemical stability of polydimethylsiloxane polymers and crosslinked materials made from them. Measurements have been made of the sol fraction of the crosslinked materials, and of stress relaxation during long periods of storage. The results are reported here.

2. Experimental details

(a) Materials and sample preparation

The materials employed have been described elsewhere (5). One was polydimethylsiloxane, denoted PDMS (SE-30, General Electric Company) and the other was basically similar except for the incorporation of a small amount of methylvinylsiloxane units (SE-33, General Electric Company). Both were crosslinked with dicumyl peroxide (Di-Cup R, Hercules Chemical Company).

(b) Determination of equilibrium swelling in toluene and sol content

Weighed samples of the crosslinked materials, about 1 mm thick and weighing about 0.2 g, were immersed in toluene at room temperature for 48 h. The toluene was replaced after 24 h. The swollen samples were weighed in order to determine the amount of toluene absorbed and then dried at 80°C or at room temperature in vacuo for 16 h to determine the dry weight of the sample.

(c) Stress relaxation

A strip of crosslinked material about 90 mm long, 10 mm wide and 2 mm thick was secured with its lower end held in a fixed clamp and its upper end held in a clamp connected by a long thin wire to a force transducer. The sample was surrounded by a heated glass tube so that its temperature could be maintained at any desired level in the range 25 - 200°C. By adjusting the position of the force transducer the sample could be stretched to various extents and then held at constant elongation over long periods of time. Most of the experiments were carried out at an extension of 20%. Provision was made for a preheated stream of air or ammonia vapor to circulate around the sample.

3. Experimental results and discussion

(a) Sol formation and degree of crosslinking

Measurements of the sol fraction of lightly-crosslinked silicone rubber gave continuously-increasing values as the extraction process continued, Figure 1. This feature has been noted previously by Bueche (6). It suggests that the molecular network decomposes slowly with the passage of time to form additional uncrosslinked material.

As shown in Figure 2, when an extracted sample is stored under relatively-mild conditions, a considerable amount of new soluble material is generated. This process is accelerated somewhat at higher temperatures, and strongly by the presence of ammonia vapor. As it does not appear to take place under dry conditions, it is attributed to a hydrolytic decomposition, catalyzed by ammonia.

Similar, but much smaller, effects were observed with the vinyl-containing PMVS polymer, crosslinked to different degrees. The measured amounts of soluble material after storage under various conditions are given in Table 1.

It was noticed that removal of the newly-formed soluble material by extraction caused an increased rate of formation of sol, Figure 3. Apparently, an equilibrium is established between the sol and gel fractions and when the soluble portion is removed decomposition proceeds further to replace it.

Simultaneously with the formation of new soluble material the equilibrium degree of swelling of the materials increases slightly, Table 2, suggesting again that this polymer is chemically unstable

under relatively mild storage conditions. Although decomposition of silicone rubber has been noted previously at relatively high temperatures (7-9), and attributed to hydrolysis, it has not previously been reported to take place under relatively mild conditions, at least as far as the present authors are aware.

(b) Stress relaxation and permanent set

Continued relaxation of the tensile stress in crosslinked materials held in the stretched state reflects changes in the network structure. Some relaxation is associated solely with physical processes such as the slow rearrangement of entangled molecules. When a stretched strip of lightly-crosslinked PDMS was exposed to ammonia vapor, the tensile stress decreased by about 10 per cent in a period of an hour or two, Figure 4. This change is attributed solely to a physical process, i.e., the uptake of ammonia by the elastomer. When the surrounding ammonia gas stream was removed and the absorbed ammonia slowly diffused out of the stretched strip, then the tensile stress returned to its original level, Figure 4.

Nevertheless, continued relaxation of stress due to network decomposition was evident at long times, at elevated temperatures, and especially in the presence of ammonia vapor, Figure 5. In this case, when the ammonia was removed after prolonged exposure, then the stress no longer returned to the level expected from air exposure, Figure 5. Moreover, the continued relaxation in air, and accelerated relaxation in ammonia, suggests that virtually all of the network chains would be broken after about 1,000 h in air and 100 h in ammonia. Thus, the decomposition process at 110°C is relatively rapid and extensive.

However, the materials after a substantial degree of stress relaxation had occurred, i.e., when only 35-40 per cent of the initial stress remained, were found to swell in toluene to about the same extent as originally. Thus, the total density of network

chains was not significantly altered by prolonged storage. This indicates that the decomposition process leading to stress relaxation must be primarily a process of bond interchange rather than bond scission, probably catalyzed by moisture and by residues of the catalysts introduced for polymerization. This conclusion is supported by the rather large amount of permanent set, about 50 per cent, shown by the same samples when the tensile stress was removed.

Silanol groups in polydimethylsiloxane polymers may be partly responsible for the relatively-facile bond rearrangement and decomposition that has been observed. These groups are relatively reactive. Together with ionic impurities or catalyst residues, they could well reduce the stability of unfilled silicone polymers (7, 9-12). It should be noted that the materials used for relaxation experiments were unextracted and so contained impurities arising from both the polymerization and crosslinking reactions. It appears that this sensitivity towards impurities is greatly reduced in the presence of fillers, as is usually the case in commercial formulations (13).

Evidence for the presence of silanol groups in the original polymer was obtained by reacting PDMS with tetraethoxysilane, yielding a substantial amount, 76 per cent, of gelled polymer. Thus, there must have been at least one silanol group on each polymer molecule in order to be able to achieve this high degree of gelation.

An attempt was also made to block these OH groups by reacting PDMS with hexamethyldisilazane to yield trimethylsiloxy groups in their place (5). Crosslinked samples made from this modified polymer were found to generate soluble material to a considerably smaller degree on prolonged storage, Figure 6, indicating an increased stability. However, the relaxation of stress at 110°C and in the presence of ammonia vapor was found to take place to the same degree and at much the same speed as for the corresponding unmodified material.

Thus, it appears that while OH groups present in the original polymer play an important role in the processes leading to the formation of soluble material, they do not appear to affect significantly the process, probably bond-interchange, that is responsible for the observed relaxation of stress.

4. Conclusions

Evidence has been put forward for slow hydrolytic decomposition of polydimethylsiloxane under relatively mild conditions. The amount of soluble material in lightly-crosslinked materials increases continuously and the stress in stretched strips relaxes continuously. These processes are catalyzed by the presence of moisture, and ammonia, and by raising the temperature. Moreover, when the number of silanol groups in the polymer was reduced, the stability was found to be increased. This suggests that silanol groups in polydimethylsiloxane polymers play an important role in initiating the hydrolytic reactions that are inferred to be responsible for stress-relaxation, sol formation, and chemical bonding to silica fillers (14) or to OH-containing substrates (5).

Acknowledgements

This work forms part of a program of research on adhesion supported by the Office of Naval Research (Contract N00014-76-C-0408). Additional support from Lord Kinematics Division of Lord Corporation is also acknowledged.

References

1. W. Noll, "Chemistry and Technology of Silicones," Academic Press, N. Y., 1968.
2. F. M. Lewis, Rubb. Chem. Technol., 35, 1222 (1962).
3. E. L. Warrick, O. R. Pierce, K. E. Polmanteer and J. C. Saam: Rubb. Chem. Technol., 52, 437, (1979).
4. B. Dolezel, L. Adamirova and Z. Naprstek, Plasty Kaucuk, 17, 276 (1980).
5. A. N. Gent and P. Vondracek, J. Appl. Polymer Sci., in press.
6. A. M. Bueche, J. Polymer Sci., 15, 105 (1955).
7. A. C. Martellock, Division of Polymer Chemistry, ACS, Boston, April 10, 1959.
8. D. K. Thomas, Polymer, 7, 99 (1966).
9. R. G. Osthoff, A. M. Bueche and W. T. Grubb, J. Amer. Chem. Soc., 76, 4659 (1954)
10. J. M. Nielsen, J. Appl. Polymer Science: Applied Polymer Symposia, 35, 223 (1979).
11. E. G. Rochow, Chemistry of the Silicones, 2nd ed., Wiley, New York, 1951.
12. N. Grassie and I. G. MacFarlane, European Polymer J., 14 875 (1978).
13. J. R. Falender, Private communication.
14. Li Yu-Fu, Xia Yong-Xia, Xu Gong-Peng and Li Guang-Liang, J. Polymer Science: Polymer Chem. Ed., 19, 3096 (1981).

Table 1. Weight fraction of soluble material (%) formed in
previously-extracted samples of PMVS silicone rubber
when stored under various conditions

<u>Storage conditions</u>	<u>Storage time (h)</u>	<u>Samples</u>	
		Crosslinked with 0.025% DCP	Crosslinked with 0.5% DCP
Air, 25°C	48	0.06	0.09
	240	0.01	0.00
	410	0.00	--
Air, 135°C	48	0.1	0.12
	240	0.22	0.00
	410	0.29	--
NH ₄ OH, 25°C	48	0.20	0.21
	240	0.33	0.15
	410	0.68	0.33

Table 2. Equilibrium volume swelling ratios in toluene after storage for three weeks under various conditions.

<u>Storage Conditions</u>	<u>Samples</u>		
	PMVS (0.025% DCP)	PMVS (0.5% DCP)	PDMS (2% DCP)
(Initial values)	(7.85)	(4.55)	(9.5)
Air, 25°C	-	4.65	-
Air, 135°C	9.1	-	-
NH ₄ OH, 25°C	9.0	4.65	11.25


Figure Captions

- Figure 1. Weight loss ΔW of a lightly-crosslinked PDMS material after extraction with toluene for various periods. Cold extraction, O; hot (Soxhlet) extraction, Δ .
- Figure 2. Soluble fraction ΔS generated in a previously-extracted sample of a lightly-crosslinked PDMS material by exposure for various periods to different environments.
- Figure 3. Soluble fraction S generated in a previously-extracted sample of a lightly-crosslinked PDMS material by exposure to ammonia vapor at room temperature, O. Sample extracted after 200 h exposure and then re-exposed, \bullet .
- Figure 4. Relaxation of tensile stress f , relative to the initial value f_0 , for a lightly-crosslinked sample of PDMS at 70°C. Air atmosphere, O; NH_3 admitted after 1 h, \bullet ; NH_3 atmosphere removed after 3 h, \bullet .

Figure 5. Relaxation of tensile stress \underline{f} , relative to the initial value \underline{f}_0 , for a lightly-crosslinked sample of PDMS at 110°C in air, 0; in ammonia, 0, ●, after ammonia was removed, ●.

Figure 6. Soluble fraction \underline{S} generated in lightly-crosslinked samples of treated (●) and untreated (0) PDMS on exposure to ammonia vapor at room temperature.

11

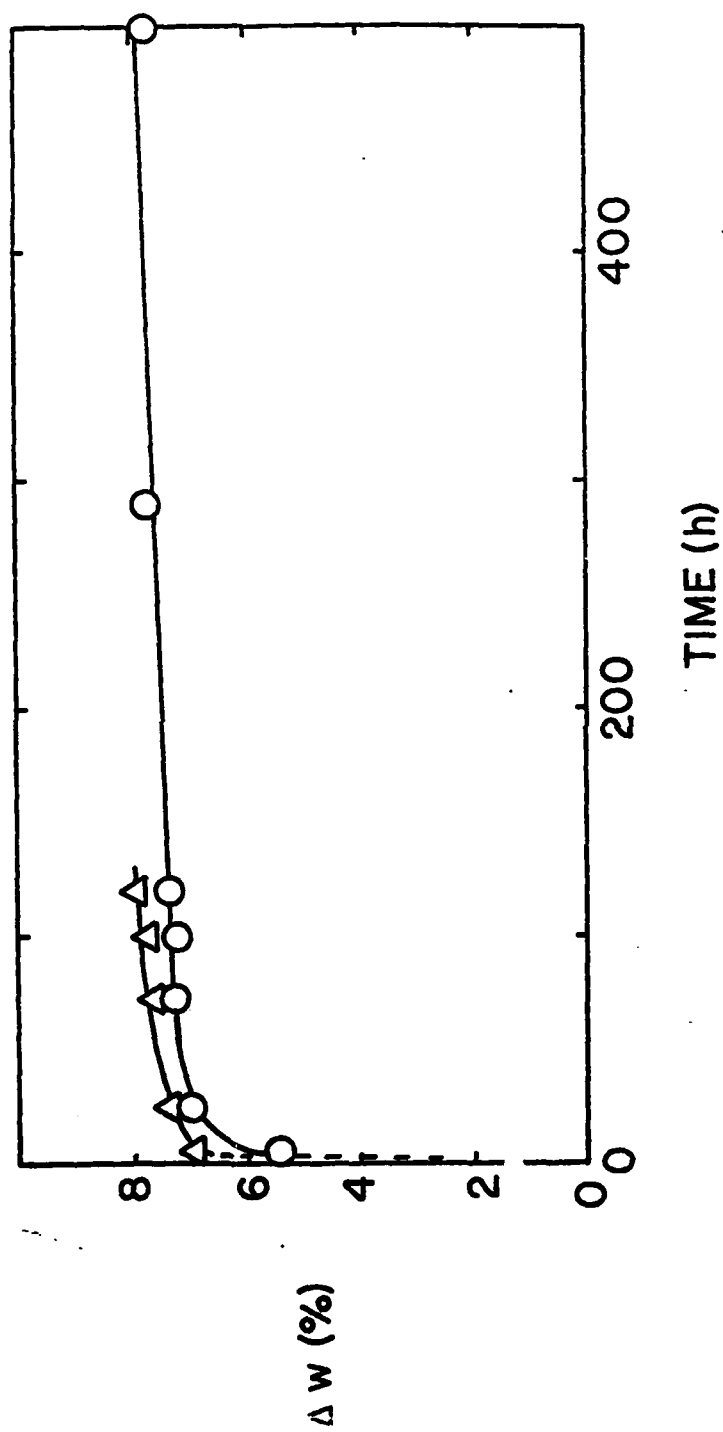FIGURE 1



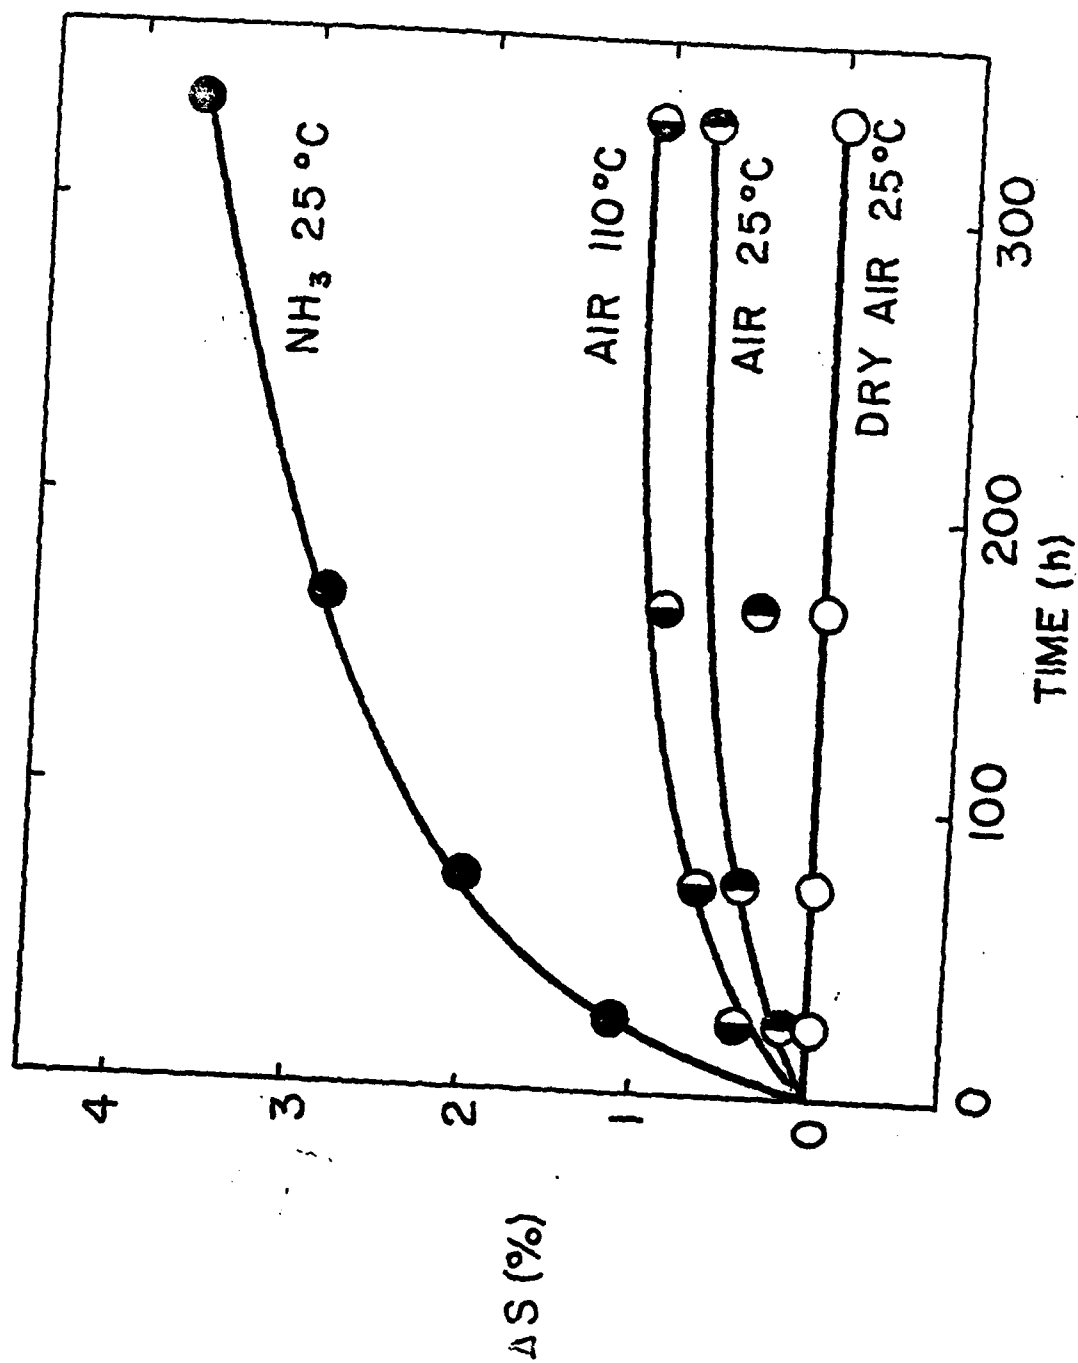



FIGURE 2

FIGURE 3

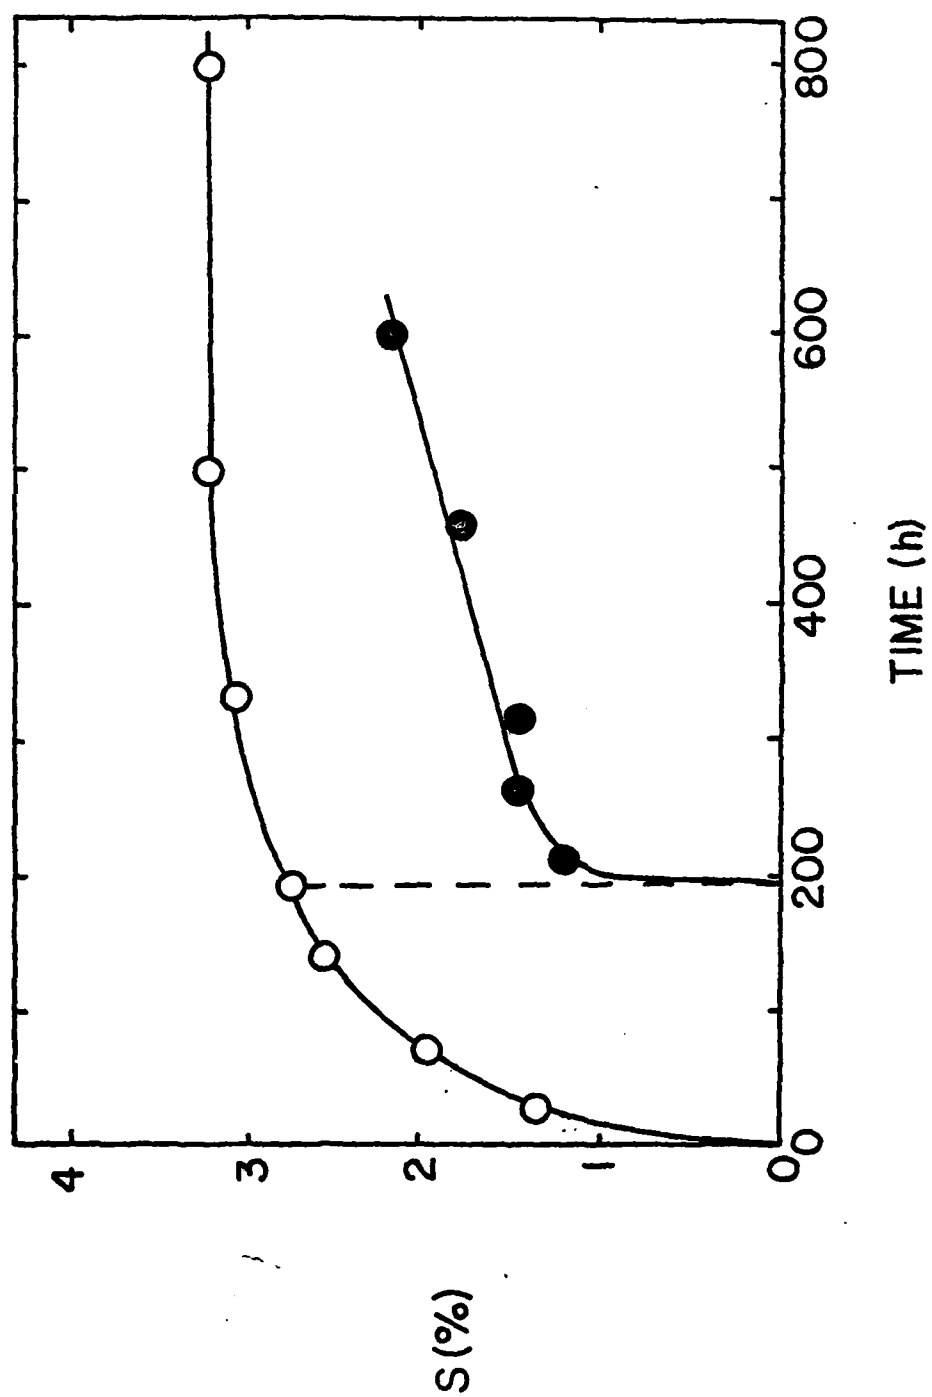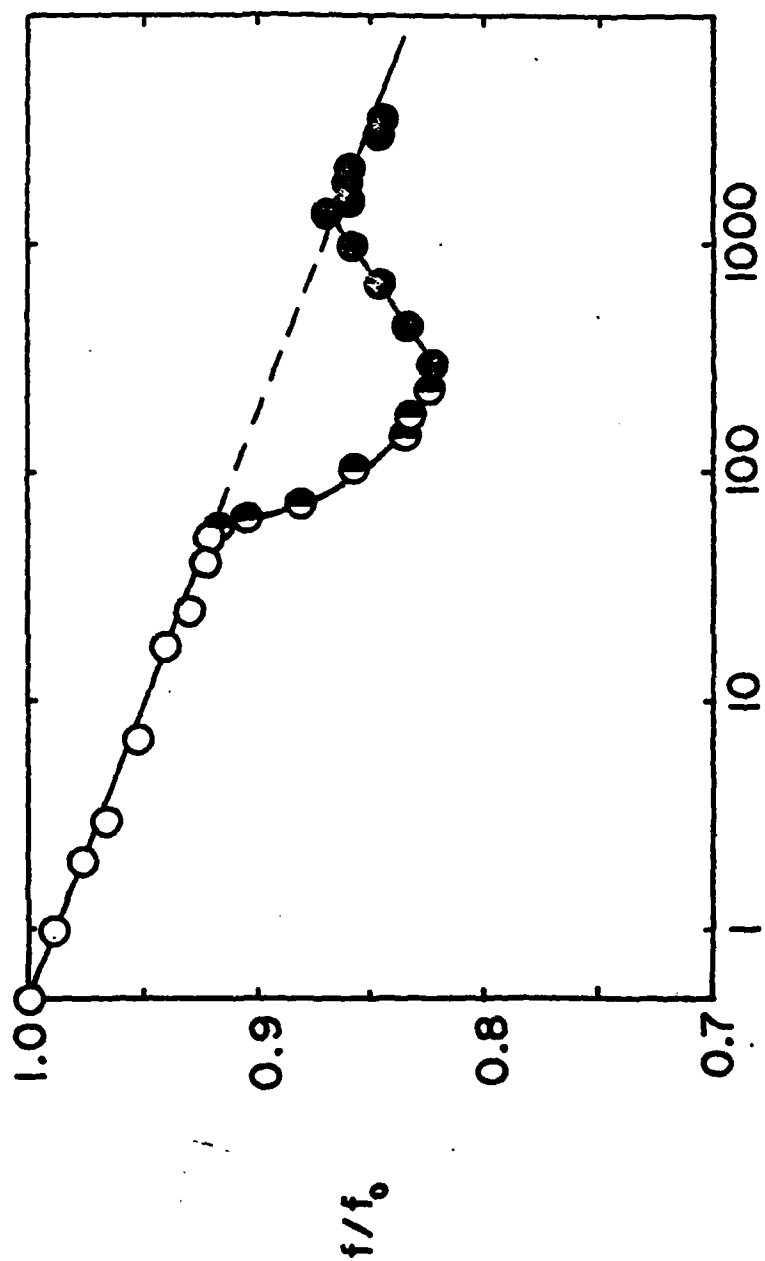


TIME (min)

FIGURE 4

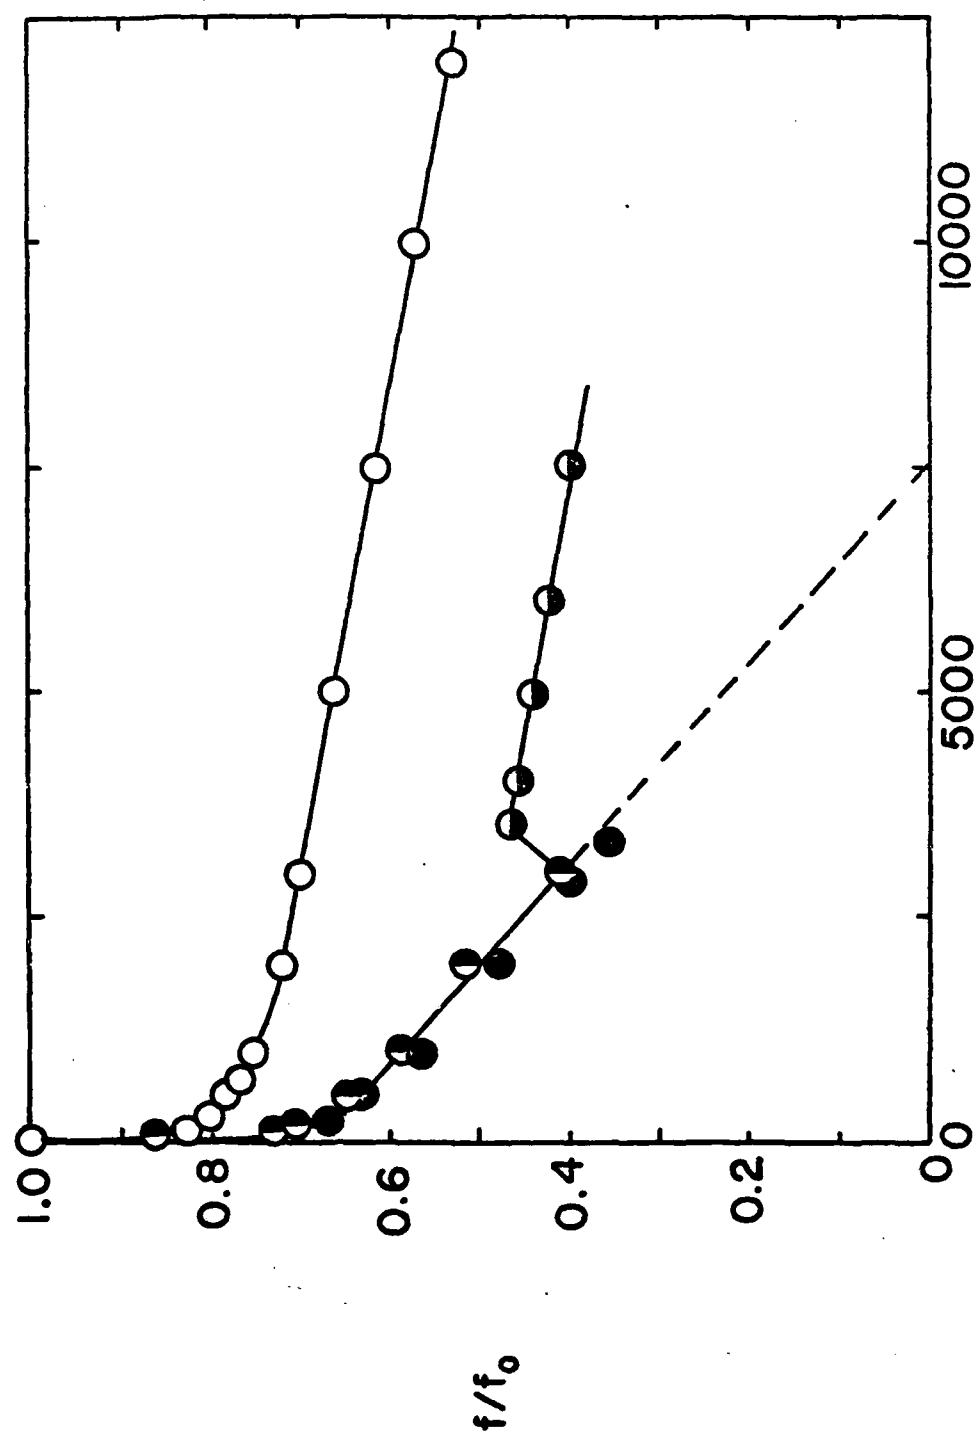

TIME (min)

FIGURE 5

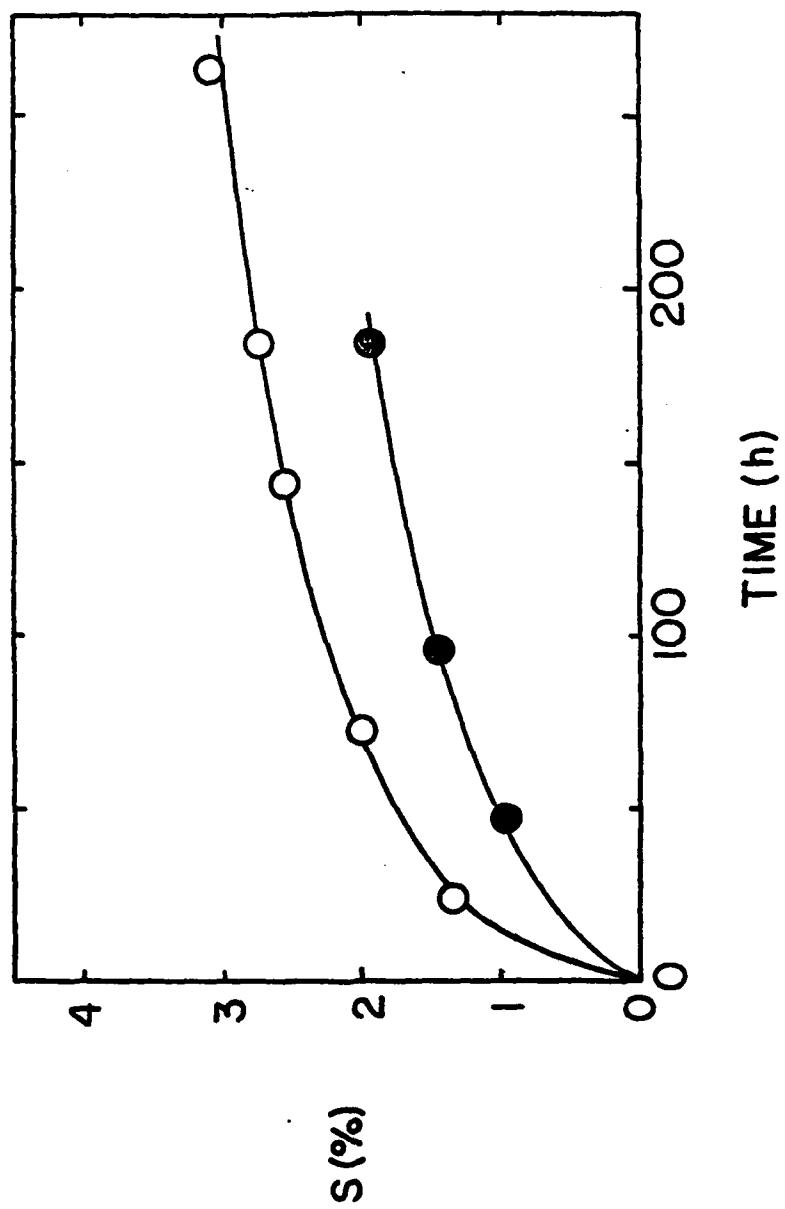FIGURE 6

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. L.V. Schmidt Assistant Secretary of the Navy (R,E, and S) Room 5E 731 Pentagon Washington, D.C. 20350	1	Dr. F. Roberto Code AFRPL MKPA Edwards AFB, CA 93523	1
Dr. A.L. Slafkosky Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1	Dr. L.H. Caveny Air Force Office of Scientific Research Directorate of Aerospace Sciences Bolling Air Force Base Washington, D.C. 20332	1
Dr. Richard S. Miller Office of Naval Research Code 413 Arlington, VA 22217	10	Mr. Donald L. Ball Air Force Office of Scientific Research Directorate of Chemical Sciences Bolling Air Force Base Washington, D.C. 20332	1
Mr. David Siegel Office of Naval Research Code 260 Arlington, VA 22217	1	Dr. John S. Wilkes, Jr. FJSRL/NC USAF Academy, CO 80840	1
Dr. R.J. Marcus Office of Naval Research Western Office 1030 East Green Street Pasadena, CA 91106	1	Dr. R.L. Lou Aerojet. Strategic Propulsion Co. P.O. Box 15699C Sacramento, CA 95813	1
Dr. Larry Peebles Office of Naval Research East Central Regional Office 666 Summer Street, Bldg. 114-D Boston, MA 02210	1	Dr. V.J. Keenan Anal-Syn Lab Inc. P.O. Box 547 Paoli, PA 19301	1
Dr. Phillip A. Miller Office of Naval Research San Francisco Area Office One Hallidie Plaza, Suite 601 San Francisco, CA 94102	1	Dr. Philip Howe Army Ballistic Research Labs ARRADCOM Code DRDAR-BLT Aberdeen Proving Ground, MD 21005	1
Mr. Otto K. Heiney AFATL - DLDL Elgin AFB, FL 32542	1	Mr. L.A. Watermeier Army Ballistic Research Labs ARRADCOM Code DRDAR-BLI Aberdeen Proving Ground, MD 21005	1
Mr. R. Geisler ATTN: MKP/MS24 AFRPL Edwards AFB, CA 93523	1	Dr. W.W. Wharton Attn: DRSM-RKL Commander U.S. Army Missile Command Redstone Arsenal, AL 35898	1

DYN

6/81

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. R.G. Rhoades Commander Army Missile Command DRSMI-R Redstone Arsenal, AL 35398	1	Dr. E.H. Debutts Hercules Inc. Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. W.D. Stephens Atlantic Research Corp. Pine Ridge Plant 7511 Wellington Rd. Gainesville, VA 22065	1	Dr. James H. Thacher Hercules Inc. Magna Baccus Works P.O. Box 98 Magna, UT 84044	1
Dr. A.W. Barrows Ballistic Research Laboratory USA ARRADCOM ORDAR-BLP Aberdeen Proving Ground, MD 21005	1	Mr. Theodore M. Gilliland Johns Hopkins University APL Chemical Propulsion Info. Agency Johns Hopkins Road Laurel, MD 20810	1
Dr. C.M. Frey Chemical Systems Division P.O. Box 358 Sunnyvale, CA 94086	1	Dr. R. McGuire Lawrence Livermore Laboratory University of California Code L-324 Livermore, CA 94550	1
Professor F. Rodriguez Cornell University School of Chemical Engineering Olin Hall, Ithaca, N.Y. 14853	1	Dr. Jack Linsk Lockheed Missiles & Space Co. P.O. Box 504 Code Org. 83-10, Bldg. 154 Sunnyvale, CA 94088	1
Defense Technical Information Center DTIC-DDA-2 Cameron Station Alexandria, VA 22314	12	Dr. B.G. Craig Los Alamos National Lab P.O. Box 1663 NSP/DOD, MS-245 Los Alamos, NM 87545	1
Dr. Rocco C. Musso Hercules Aerospace Division Hercules Incorporated Alleghany Ballistic Lab P.O. Box 210 Washington, D.C. 21502	1	Dr. R.L. Rabie WX-2, MS-952 Los Alamos National Lab. P.O. Box 1663 Los Alamos NM 37545	1
Dr. Ronald L. Simmons Hercules Inc. Eglin AFATL/DLCL Eglin AFB, FL 32542	1	Dr. R. Rogers, WX-2 Los Alamos Scientific Lab. P.O. Box 1663 Los Alamos, NM 87545	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. R. Brown Naval Air Systems Command Code 330 Washington, D.C. 20361	1	Dr. J. Schnur Naval Research Lab. Code 6510 Washington, D.C. 20375	1
Dr. H. Rosenwasser Naval Air Systems Command AIR-310C Washington, D.C. 20360	1	Mr. R. Beauregard Naval Sea Systems Command SEA 64E Washington, D.C. 20362	1
Mr. B. Sobers Naval Air Systems Command Code 03P25 Washington, D.C. 20360	1	Mr. G. Edwards Naval Sea Systems Command Code 62R3 Washington, D.C. 20362	1
Dr. L.R. Rothstein Assistant Director Naval Explosives Dev. Engineering Dept. Naval Weapons Station Yorktown, VA 23691	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, PA 19112	1
Dr. Lionel Dickinson Naval Explosive Ordnance Disposal Tech. Center Code D Indian Head, MD 20640	1	Dr. H.G. Adolph Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1
Mr. C.L. Adams Naval Ordnance Station Code PM4 Indian Head, MD 20640	1	Dr. T.D. Austin Naval Surface Weapons Center Code R16 Indian Head, MD 20640	1
Mr. S. Mitchell Naval Ordnance Station Code 5253 Indian Head, MD 20640	1	Dr. T. Hall Code R-11 Naval Surface Weapons Center White Oak Laboratory Silver Spring, MD 20910	1
Dr. William Tolles Dean of Research Naval Postgraduate School Monterey, CA 93940	1	Mr. G.L. Mackenzie Naval Surface Weapons Center Code R101 Indian Head, MD 20640	1
Naval Research Lab. Code 6100 Washington, D.C. 20375	1	Dr. K.F. Mueller Naval Surface Weapons Center Code R11 White Oak Silver Spring, MD 20910	1

DYN

6/81

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Mr. J. Murrin Naval Sea Systems Command Code 62R2 Washington, D.C. 20362	1	Dr. A. Nielsen Naval Weapons Center Code 385 China Lake, CA 93555	1
Dr. D.J. Pastine Naval Surface Weapons Center Code R04 White Oak Silver Spring, MD 20910	1	Dr. R. Reed, Jr. Naval Weapons Center Code 388 China Lake, CA 93555	1
Mr. L. Roslund Naval Surface Weapons Center Code R122 White Oak, Silver Spring MD 20910	1	Dr. L. Smith Naval Weapons Center Code 3205 China Lake, CA 93555	1
Mr. M. Stosz Naval Surface Weapons Center Code R121 White Oak Silver Spring, MD 20910	1	Dr. B. Douda Naval Weapons Support Center Code 5042 Crane, Indiana 47522	1
Dr. E. Zimmet Naval Surface Weapons Center Code R13 White Oak Silver Spring, MD 20910	1	Dr. A. Faulstich Chief of Naval Technology MAT Code 0716 Washington, D.C. 20360	1
Dr. D. R. Derr Naval Weapons Center Code 388 China Lake, CA 93555	1	LCDR J. Walker Chief of Naval Material Office of Naval Technology MAT, Code 0712 Washington, D.C. 20360	1
Mr. Lee N. Gilbert Naval Weapons Center Code 3205 China Lake, CA 93555	1	Mr. Joe McCartney Naval Ocean Systems Center San Diego, CA 92152	1
Dr. E. Martin Naval Weapons Center Code 3858 China Lake, CA 93555	1	Dr. S. Yamamoto Marine Sciences Division Naval Ocean Systems Center San Diego, CA 91232	1
Mr. R. McCarter Naval Weapons Center Code 3272 China Lake, CA 93555	1	Dr. G. Bosmajian Applied Chemistry Division Naval Ship Research & Development Center Annapolis, MD 21401	1
		Dr. H. Shuey Rohn and Haas Company Huntsville, Alabama 35801	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. J.F. Kincaid Strategic Systems Project Office Department of the Navy Room 901 Washington, D.C. 20376	1	Dr. C.W. Vriesen Thiokol Elkton Division P.O. Box 241 Elkton, MD 21921	1
Strategic Systems Project Office Propulsion Unit Code SP2701 Department of the Navy Washington, D.C. 20376	1	Dr. J.C. Hinshaw Thiokol Wasatch Division P.O. Box 524 Brigham City, Utah 84302	1
Mr. E.L. Throckmorton Strategic Systems Project Office Department of the Navy Room 1048 Washington, D.C. 20376	1	U.S. Army Research Office Chemical & Biological Sciences Division P.O. Box 12211 Research Triangle Park NC 27709	1
Dr. D.A. Flanigan Thiokol Huntsville Division Huntsville, Alabama 35807	1	Dr. R.F. Walker USA ARRADCOM ORDAR-LCE Dover, NJ 07801	1
Mr. G.F. Mangum Thiokol Corporation Huntsville Division Huntsville, Alabama 35807	1	Dr. T. Sinden Munitions Directorate Propellants and Explosives Defence Equipment Staff British Embassy 3100 Massachusetts Ave. Washington, D.C. 20008	1
Mr. E.S. Sutton Thiokol Corporation Elkton Division P.O. Box 241 Elkton, MD 21921	1	LTC B. Loving AFROL/LK Edwards AFB, CA 93523	1
Dr. G. Thompson Thiokol Wasatch Division MS 240 P.O. Box 524 Brigham City, UT 84302	1	Professor Alan N. Gent Institute of Polymer Science University of Akron Akron, OH 44325	1
Dr. T.F. Davidson Technical Director Thiokol Corporation Government Systems Group P.O. Box 9253 Ogden, Utah 84409	1	Mr. J. M. Frankle Army Ballistic Research Labs ARRADCOM Code ORDAR-BLI Aberdeen Proving Ground, MD 21005	1

DISTRIBUTION LIST

	<u>No. Copies</u>		<u>No. Copies</u>
Dr. Ingo W. May Army Ballistic Research Labs ARRADCOM Code ORDAR-BLI Aberdeen Proving Ground, MD 21005	1	Dr. J. P. Marshall Dept. 52-35, Bldg. 204/2 Lockheed Missile & Space Co. 3251 Hanover Street Palo Alto, CA 94304	1
Professor N.W. Tschoegl California Institute of Tech Dept. of Chemical Engineering Pasadena, CA 91125	1	Ms. Joan L. Janney Los Alamos National Lab Mail Stop 920 Los Alamos, NM 87545	1
Professor M.D. Nicol University of California Dept. of Chemistry 405 Hilgard Avenue Los Angeles, CA 90024	1	Dr. J. M. Walsh Los Alamos Scientific Lab Los Alamos, NM 87545	1
Professor A. G. Evans University of California Berkeley, CA 94720	1	Professor R. W. Armstrong Univ. of Maryland Department of Mechanical Eng. College Park, MD 20742	1
Professor T. Litovitz Catholic Univ. of America Physics Department 520 Michigan Ave., N.E. Washington, D.C. 20017	1	Prof. Richard A. Reinhardt Naval Postgraduate School Physics & Chemistry Dept. Monterey, CA 93940	1
Professor W. G. Knauss Graduate Aeronautical Lab California Institute of Tech. Pasadena, CA 91125	1	Dr. R. Bernecker Naval Surface Weapons Center Code R13 White Oak, Silver Spring, MD 20910	1
Professor Edward Price Georgia Institute of Tech. School of Aerospace Engin. Atlanta, Georgia 30332	1	Dr. M. J. Kamlet Naval Surface Weapons Center Code R11 White Oak, Silver Spring, MD 20910	1
Dr. Kenneth O. Hartman Hercules Aerospace Division Hercules Incorporated P.O. Box 210 Cumberland, MD 21502	1	Professor J. D. Achenbach Northwestern University Dept. of Civil Engineering Evanston, IL 60201	1
Dr. Thor L. Smith IBM Research Lab 042.282 San Jose, CA 95193	1	Dr. N. L. Basdekas Office of Naval Research Mechanics Program, Code 432 Arlington, VA 22217	1
		Professor Kenneth Kuo Pennsylvania State Univ. Dept. of Mechanical Engineering University Park, PA 16802	1

DYN

6/81

DISTRIBUTION LIST

	<u>No. Copies</u>	<u>No. Copies</u>
Dr. S. Sheffield Sandia Laboratories Division 2513 P.O. Box 5800 Albuquerque, NM 87185	1	
Dr. M. Farber Space Sciences, Inc. 135 Maple Avenue Monrovia, CA 91016	1	
Dr. Y. M. Gupta SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Mr. M. Hill SRI International 333 Ravenswood Avenue Menlo Park, CA 94025	1	
Professor Richard A. Schapery Texas A&M Univ. Dept of Civil Engineering College Station, TX 77843	1	
Dr. Stephen Swanson Univ. of Utah Dept. of Mech. & Industrial Engineering MEB 3008 Salt Lake City, UT 84112	1	
Mr. J. D. Byrd Thiokol Corp. Huntsville Huntsville Div. Huntsville, AL 35807	1	
Professor G. D. Duval Washington State University Dept. of Physics Pullman, WA 99163	1	
Prof. T. Dickinson Washington State University Dept. of Physics Pullman, WA 99163	1	

DATE
ILMED
8